

# High Pressure Fuel Injection Systems: Shot Peening and its Effect on Residual Stress

Rachel Butler, Yuheng Du, Heather Macdonald, Kerui Sun  
 Faculty Advisor: Professor John Blendell  
 Industrial Sponsors: Brian Wright, Andrew Armuth

Almen Intensity and residual stress were characterized by varying shot peening parameters and measured by X-ray diffraction (XRD). Hardness, surface roughness, and residual stress (RS) depth profiles were conducted on 4140 and 52100 steels as well as Almen strips to analyze the effects of variation in shot media size, shot pressure, and shot type. Hardness variation was seen to be the most influential variable in roughness and RS.

This work is sponsored by Cummins Fuel Systems, Columbus, IN.




## Project Background

Cummins Fuel Systems designs and manufactures high pressure diesel fuel systems that need to survive high cyclic pressures during operation. Shot peening is employed as a surface strengthening technique on pressure bearing surfaces of fuel system components where fatigue failure, due to alternating pressure, is most likely to occur. Shot peening induces subsurface compressive residual stresses (RS) that oppose the tensile stresses which would otherwise contribute to fatigue.

XRD techniques are capable of directly measuring crystallographic lattice strain which can be translated to stress by the  $\sin^2\psi$  method. However, because XRD cannot be performed on small inner diameters such as that of fuel system components, Almen Intensity is instead used to monitor the shot peening process. The main objective of this study is to correlate the stresses measured with XRD to the Almen Intensity and determine the effects of altering shot peening parameters.

## Experimental Procedure

Steel coupons (76.1mm x 18.95mm x 6.35mm) of 4140 (40-45 HRC) and 50-55 HRC) and 52100 (58-62 HRC) were shot peened by MIC. Peening was performed using a  $\frac{3}{8}$ " nozzle set perpendicular to the coupon and at 7" spacing. Nozzle oscillation speed across the coupon was 24 in/min for metallic shot and 12 in/min for ceramic shot until 100% coverage was achieved (3-8 passes). Single and dual shot media sequences were studied. S170-H and S70-H cast steel shot were utilized in single peening; dual peening experiments used S110-H and S70-H cast steel shots sequentially or S170-H cast steel shot and Z150 ceramic shot sequentially. S170-H and S70-H were chosen for comparison to the incumbent process; dual peening and ceramic shot were chosen for investigative data gathering.

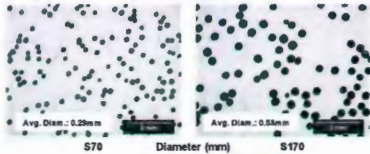


The increased diameter size increased the potential to input more force into the surface of the sample, with residual stress.

Samples were then examined via optical microscopy, profilometry, hardness, and XRD. XRD was performed using a chromium x-ray tube with vanadium filter, set to 25kV and 0.8mA. SaraTEC Analysis Manager v1.3.37 software calculated RS values using 4340 50 HRC for the material constant. This software also compiled RS depth profiles using XRD measurements obtained after incrementally electropolishing into the coupons. Three-dimensional optical profilometry (ZeScopeTM) gathered five surface roughness measurements across each sample.

Almen Intensity is the arc height measurement of thin, standardized, steel strips. If a sample is sufficiently thin, the compressive RS imparted by peening creates concave bending of the sample which is measured by regulated gauges. (SAE J443)

## Results & Discussion



### Roughness



4140 40-45 HRC (left), 52100 58-62 HRC (right).

Hardness was the most influential variable to surface roughness as shown by the 40-45 HRC sample. Changes in air pressure showed only slight differences in roughness. From


only changing the hardness, softer coupons displayed rougher surfaces after peening. However, the 75 psi, S170+Ceramic dual-peened sample with 58-62 HRC displayed a higher roughness value than expected. This was due to debris on the sample's surface increasing the distance between the highest and lowest measured points and thereby increasing the mean  $R_a$  value.

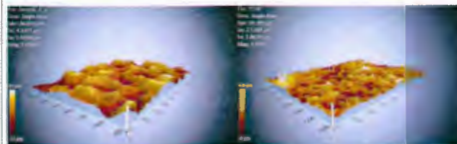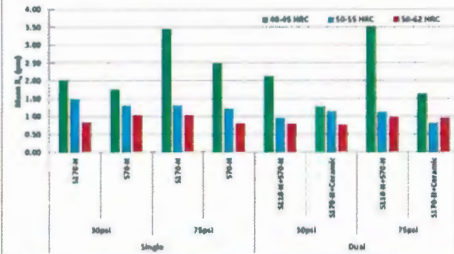


A S170-single peened (left) vs. a S170+Ceramic-dual peened (right) sample showed decreased roughness. The second, smaller ceramic deformed the surface more uniformly, resulting in a smoother surface.

### Residual Stress & Almen Intensity (AI)


The initial hypothesis was that harder materials would exhibit larger RS due to deformation resistance. Results showed that the 50-55 HRC samples exhibited the largest compressive RS as seen in the depth profile.

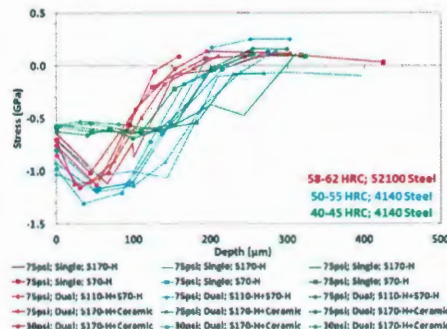


Almen Intensity values increased with pressure and media size. The ceramic shot was harder than the steel shot used, but due to mass decrease, the Almen Intensity was the lowest.

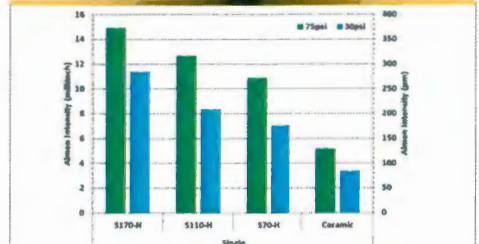

Surface RS decreased as air pressure increased.

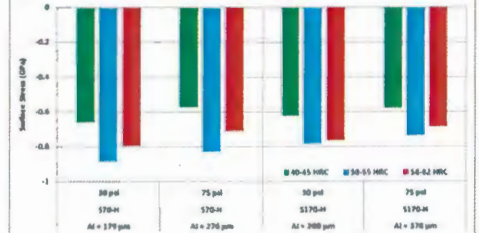

Stress integral was defined by the definite integral of the depth profile for compressive stresses beneath the x-axis. This integral increased with shot size and corresponded to an increase in Almen Intensity implying that Almen Intensity can be correlated to RS.

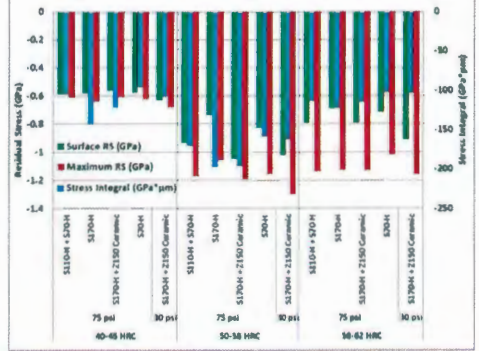

## Conclusions & Future Work

- Coupon hardness was the most influential parameter regarding material response. The 40-45 HRC material was unable to retain induced stresses.
- 52100 (58-62 HRC) contains carbides that may act to impede dislocation motion. When compared to 4140 (50-55 HRC), 52100 (58-62 HRC) may require a higher intensity shot peening process to induce the same RS magnitude.
- Future work should include measuring RS after peening of reduced-carbide 52100 as well as 4140 and 52100 samples of the same hardness.
- Immediate future work should include creating RS depth profiles of coupons peened at 30psi to relate air pressure to maximum compressive RS and area under the depth profile curve.

## Acknowledgement

Metal Improvement Company (MIC), a division of Curtiss-Wright Corporation, was critical in the development and execution of this project.